

सिपेट : इंस्टिट्यूट ऑफ प्लास्टिक्स टेक्नॉलॉजी

(रसायन एवं उर्वरक मंत्रालय, भारत सरकार)

गिण्टी, चेन्नै - 600 032.

फोन : 91-44-2225 4701-6 फैक्स : 91-44-22254707

ई-मेल : chennai@cipet.gov.in वेबसाइट : www.cipet.gov.in



CIPET सिपेट  
probe - perform - practice - Plastics

CIPET : INSTITUTE OF PLASTICS TECHNOLOGY

(Ministry of Chemicals & Fertilizers, Govt. of India)

Guindy, Chennai - 600 032.

Tel : 91-44-2225 4701-6 Fax : 91 - 44 - 22254707

E-mail : chennai@cipet.gov.in Website : www.cipet.gov.in

को जारी / Issued to :

**M/s. Unique Multi Films Virudhunagar (P) Ltd.,**

**No. 7/152/2, Perali Road,  
Virudhunagar – 626 001.**

**परीक्षण रिपोर्ट  
TEST REPORT**

क्र.सं / SI. No. **22139**

रिपोर्ट सं / REPORT NO. : **58585**

Pages.....Nos. Part A,B,C & D

दिनांक / Date : **09.09.2019**

संदर्भ / Ref. : **Dated: 07.10.2018**

परीक्षण मानक स्तर के अनुसार परीक्षण रिपोर्ट / TEST REPORT AS PER TEST STANDARD : Refer Part C

**भाग - क / PART - A**

**प्रस्तुत सैंपिल का विवरण / PARTICULARS OF SAMPLE SUBMITTED**

अ) सैंपिल का नाम / a) Name of the Sample	:	Film Sample -as stated by the party
आ) सैंपिल प्राप्त होने की तारीख / b) Date of Receipt of sample	:	10.10.2018
इ) ग्रेड/प्रकार/आकार/वर्ग / c) Grade / variety / type / size / class	:	Not applicable
ई) घोषित मूल्य / d) Declared value, If any	:	Not applicable
उ) कोड सं. / e) Code No.	:	Not applicable
ऊ) बैच सं. एवं निर्माण तारीख / f) Batch No. and Date of Manufacture:	:	Not applicable
ऋ) मात्रा / g) Quantity	:	01 Box
ए) पैकिंग की रीति / h) Mode of Packing	:	Packed in carton pack
ऐ) मोहर बंद या नहीं / i) Sealed or not	:	Not Sealed
ओ) कोई अन्य सूचना / j) Any other information	:	--

**भाग - ख / PART - B**

**अनुपूरक सूचनाएँ / SUPPLEMENTARY INFORMATIONS**

अ) सैंपिलिंग कार्यवाहियों हेतु संदर्भ / a) Reference to sampling procedure	:	Sampling not done by this lab
आ) माप करने हेतु लिए गए सहायक दस्तावेज एवं प्राप्त परिणाम b) Supporting documents for the measurement taken and result derived	:	As given in Part C
इ) संबंधित कार्य अनुदेशों में निर्धारित के अनुसार परीक्षण रीति से कोई परिवर्तन c) Deviation from the test method as prescribed in relevant work instructions, if any	:	No deviation from the standard

सिपेट : इंस्टिट्यूट ऑफ प्लास्टिक्स

(रसायन एवं उर्वरक मंत्रालय, भारत सरकार)

गिण्टी, चेन्नै - 600 032.

फोन : 91-44-2225 4701-6 फैक्स : 91-44-2225

ई-मेल : chennai@cipet.gov.in वेबसाइट : www.cipet.gov.in



CIPET सि पेट  
probe · perform · practice · Plastics

CIPET : INSTITUTE OF PLASTICS TECHNOLOGY

(Ministry of Chemicals & Fertilizers, Govt. of India)

Guindy, Chennai - 600 032.

Tel : 91-44-2225 4701-6 Fax : 91 - 44 - 22254707

E-mail : chennai@cipet.gov.in Website : www.cipet.gov.in

रिपोर्ट सं / REPORT NO. : 58585

परीक्षण रिपोर्ट  
TEST REPORT

22139

क्र.सं / Sl. No.

दिनांक / Date : 09.09.2019

भाग - ग / PART - C

परीक्षण परिणाम / TEST RESULTS

Test Duration: 11.10.2018 to 09.09.2019

Sl.No.	Property	Standard	Unit	Results obtained	Specified Requirements
1.	Material Identification by FTIR	--	--	Blend of Poly Lactic Acid (PLA) and Poly Butylene Adipate co-terephthalate (PBAT)	--
2.	Disintegration (Dry mass passing through 2mm sieve after 84 days)	ISO-17088 / IS-17088	%	91.1	Greater than 90
3.	Ultimate Aerobic Biodegradation (with reference to 100% degradation of positive reference)	ISO-17088 / IS-17088	%	90.05	Greater than 90
4.	Plant Growth study a) Rice % Seed emergence	ISO-17088 IS-17088	%	92	Greater than 90
	b) Tomato % Seed Emergence		%	93	Greater than 90

(Contd...)

2 of

*[Handwritten Signature]*



**TEST RESULTS**

Report No:

**58585**

Date:

**09.09.2019**

Sl. No.	Property	Standard	Unit	Results obtained	Specified Requirements (In India Maximum)*
5.	<b>Heavy metals concentration</b>	ISO-17088 / IS-17088	ppm		
	Arsenic (As)			0.027	20
	Copper (Cu)			1.95	500
	Nickel (Ni)			1.12	100
	Zinc (Zn)			5.57	2500
	Cobalt (Co)			1.02	--
	Chromium (Cr)			1.35	300
	Molybdenum (Mo)			0.069	--
	Mercury (Hg)			0.250	10
	Cadmium (Cd)			0.011	20
	Lead (Pb)			0.444	500
	Fluorine (F) as Fluoride			689	--
	Selenium (Se)			0.031	--

Note: BDL – Below Detection Limit, DL – Detection Limit

\*-Based on Municipal waste (Management and Handling) Rules, 1999 notified on 27<sup>th</sup> September, 1999 by Ministry of Environment and Forests, Government of India. Note that concentration of metals like cobalt, molybdenum, fluorine and selenium is not mentioned in the notification.

**PART - D**

**REMARKS - Nil**

**NOTE:**

1. The results related only to the items tested as supplied by the party.
2. The test certificate shall not be reproduced in full except without the written approval of the laboratory.

  
AUTHORISED SIGNATORY



**TR. NO. 58585**

**BIODEGRADABILITY TEST AS PER IS/ISO 17088**

**1. Sample detail: (as declared by the party):** Film Sample

**2. Material Identification by FTIR:** Blend of Poly Lactic Acid (PLA) & Poly Butylene Adipate Co Terephthalate (PBAT)

**3. Observation**

(1) Conditions of reaction mixtures

Origin of compost: Livestock excrement, municipal and vegetable waste

Reaction Temperature : 58°C (± 2°C)

Dry Solid (%) : 57.9

Volatile content (%) : 38.3

CO<sub>2</sub> evolved during first 10days in blank vessels : 68.2 mg/g of volatile content of compost

Test duration (day) : 90 days

Reference material : Cellulose

Volume of reaction vessel : 3000 ml

(2) pH of test medium

S.No.	Composting Vessel (Material with test medium)	pH(before)	pH(after)
1	Sample 1	7.5	7.3
2	Sample 2	7.5	7.2
3	Sample 3	7.5	7.2
4	Blank	7.5	7.5
5	Cellulose 1	7.5	7.3
6	Cellulose 2	7.5	7.3
7	Cellulose 3	7.5	7.4
8	Negative	7.5	7.5






**4. Result:**

Percentage biodegradation relative to positive reference

Sample (Mean of 3 replicates) : 90.05%

Positive reference cellulose (Mean of 3 replicates) : ~ 100 %

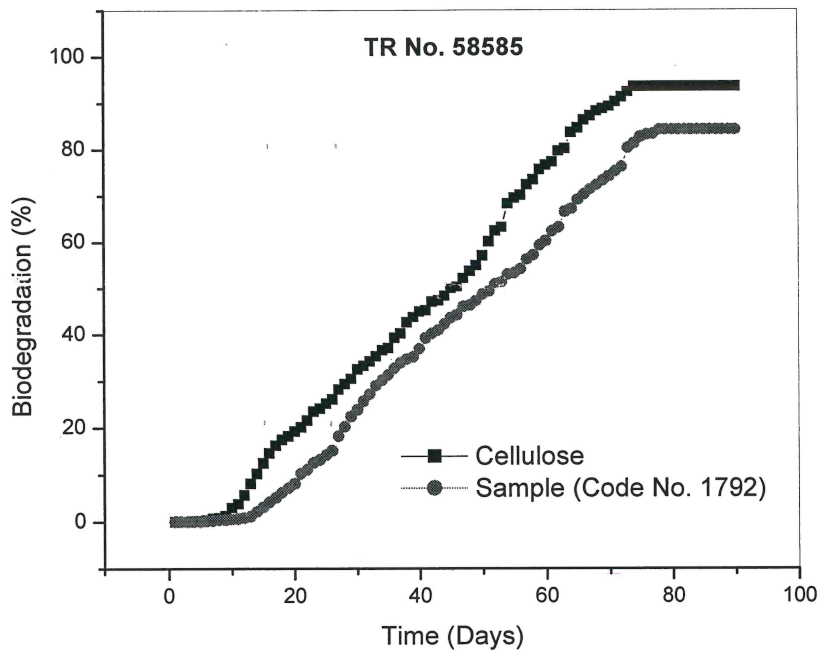

**5. Disintegration- After 12 weeks**






## 6. Visual Observation

Description	Week 1	Week 2	Week 3	Week 4/5	Week 6/7
Structure	Fine Particles	Fine Particles	Fine Particles	Fine Particles	Fine Particles
Moisture	Adequate moisture Level	Adequate moisture Level	Adequate moisture Level	Adequate moisture Level	Adequate moisture Level
Colour	Dark brown	Dark brown	Dark brown	Dark brown	Dark brown
Fungal Development	Nil	Nil	Nil	Nil	Nil
Smell	Organic/dirt like	Organic/dirt like	Organic/dirt like	Organic/dirt like	Organic/dirt like

Description	Week 8/9	Week 10/11	Week 12
Structure	Fine Particles	Fine Particles	Fine Particles
Moisture	Adequate moisture Level	Adequate moisture Level	Adequate moisture Level
Colour	Dark brown	Dark brown	Dark brown
Fungal Development	Nil	Nil	Nil
Smell	Organic/dirt like	Organic/dirt like	Organic/dirt like

## 7. Plant Growth Study

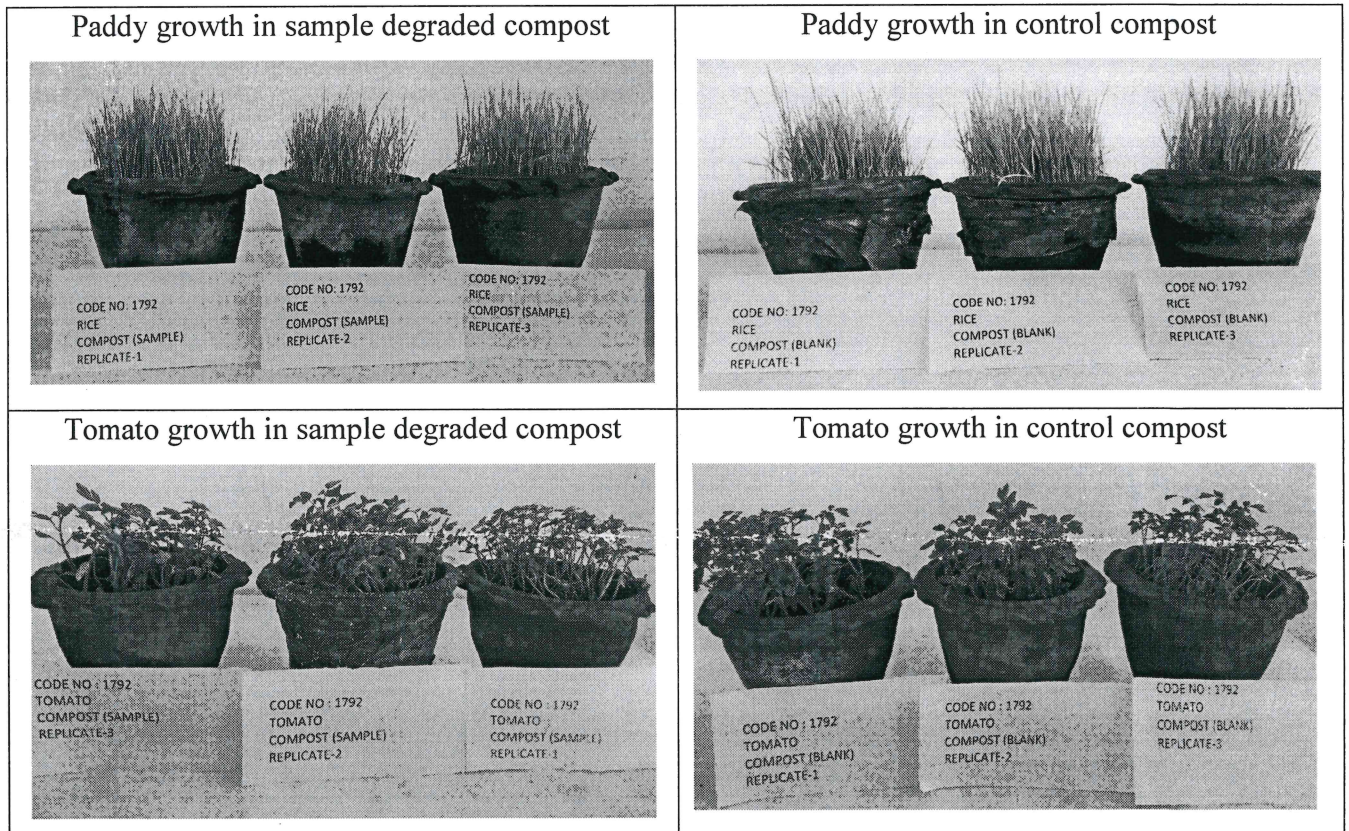

*[Handwritten Signature]*  
**Authorized Signatory**  
 Page 3 of 3